

इंटरनेट

मानक

### Disclosure to Promote the Right To Information

Whereas the Parliament of India has set out to provide a practical regime of right to information for citizens to secure access to information under the control of public authorities, in order to promote transparency and accountability in the working of every public authority, and whereas the attached publication of the Bureau of Indian Standards is of particular interest to the public, particularly disadvantaged communities and those engaged in the pursuit of education and knowledge, the attached public safety standard is made available to promote the timely dissemination of this information in an accurate manner to the public.

“जानने का अधिकार, जीने का अधिकार”

Mazdoor Kisan Shakti Sangathan

“The Right to Information, The Right to Live”

“पुराने को छोड़ नये के तरफ”

Jawaharlal Nehru

“Step Out From the Old to the New”

IS 1528-20 (1993): Methods of Sampling and Physical Tests for Refractory Materials, Part 20: Determination of Modulus of Rupture at Elevated Temperature [MTD 15: Refractories]



“ज्ञान से एक नये भारत का निर्माण”

Satyanarayan Gangaram Pitroda

“Invent a New India Using Knowledge”



“ज्ञान एक ऐसा खजाना है जो कभी चुराया नहीं जा सकता है”

Bhartrhari—Nitiśatakam

“Knowledge is such a treasure which cannot be stolen”



BLANK PAGE



**N.B. - As Per Amendment One The Standard No. is - IS 1528 : PART 20**

**IS 1528 ( Part 15 ) : 1993  
ISO 5013 : 1985  
(Reaffirmed 2004)**

**भारतीय मानक**

**उष्मासह सामग्रियों के नमूने लेने की और भौतिक परीक्षण  
पद्धतियाँ**

**भाग 15 उच्चतापमान पर सँबिदारण माँपाक ज्ञात करना**

*Indian Standard*

**METHODS OF SAMPLING AND PHYSICAL TESTS  
FOR REFRACTORY MATERIALS**

**PART 15 DETERMINATION OF MODULUS OF RUPTURE AT ELEVATED  
TEMPERATURE**

UDC 686.76 : 620.172.24

© BIS 1993

**BUREAU OF INDIAN STANDARDS  
MANAK BHAVAN, 9 BAHADUR SHAH ZAFAR MARG  
NEW DELHI 110002**

*December 1993*

**Price Group 2**

## NATIONAL FOREWORD

This Indian Standard which is identical with ISO 5013 : 1985 'Refractory products — Determination of modulus of rupture at elevated temperature', issued by the International Organization for Standardization ( ISO ), was adopted by the Bureau of Indian Standards on the recommendations of refractory Sectional Committee ( MTD 15 ) and approval of the Metallurgical Engineering Division Council.

The text of ISO Standard has been approved as suitable for publication as Indian Standard without deviations. Certain terminology and conventions are, however, not identical to those used in Indian Standards. Attention is particularly drawn to the following:

- a) Wherever the words 'ISO 5013' appear referring to this standard, they should be read as 'IS 1528 ( Part 15 )'.
- b) Comma ( , ) has been used as a decimal marker while in Indian Standards, the current practice is to use a point ( . ) as the decimal marker.

In this adopted standard reference appears to certain International Standards for which Indian Standards also exist. The corresponding Indian Standards which are to be substituted in their place are listed below along with their degree of equivalence for the edition indicated:

| <i>International Standard</i>  | <i>Indian Standard</i>   | <i>Degree of Correspondence</i> |
|--|--|---------------------------------|
| ISO 5014, Refractory products — Determination of modulus of rupture at ambient temperature | IS 1528 ( Part 5 ) : 1993 Methods of sampling and physical test for refractory material — Determination of modulus of rupture at ambient temperature | Identical                       |
| ISO 5022, Shaped refractory products — Sampling and acceptance testing                     | IS 1529 ( Part 7 ) : 1974 Methods of sampling and physical test for refractory material — Method of sampling and criteria for conformity             | Equivalent                      |

For the purpose of deciding whether a particular requirement of this standard is complied with, the final value, observed or calculated, expressing the result of a test or analysis, shall be rounded off in accordance with IS 2 : 1960 'Rules for rounding off numerical values ( revised )'. The number of significant places retained in the rounded off value should be the same as that of specified value in this standard.

# Indian Standard

## METHODS OF SAMPLING AND PHYSICAL TESTS FOR REFRACTORY MATERIALS

### PART 15 DETERMINATION OF MODULUS OF RUPTURE AT ELEVATED TEMPERATURE

#### 1 Scope and field of application

This International Standard specifies a method for the determination of the modulus of rupture of refractory products at elevated temperatures, under conditions of a constant rate of increase of stress. A method for determination of the same property at ambient temperature is given in ISO 5014.

#### 2 References

ISO 5014, *Refractory products — Determination of modulus of rupture at ambient temperatures.*<sup>1)</sup>

ISO 5022, *Shaped refractory products — Sampling and acceptance testing.*

#### 3 Definitions

**3.1 modulus of rupture:** The maximum stress that a rectangular test piece of specified dimensions can withstand when it is bent in a three-point bending device.

**3.2 test temperature:** The temperature at the mid-point of the tensile face of the test piece (see 5.3).

#### 4 Principle

**4.1** Test pieces taken from items (bricks) are heated to the test temperature. After being maintained at this temperature until a specified temperature distribution is reached, the test pieces are loaded at a constant rate of increase of tensile stress until failure occurs.

**4.2** The method relates primarily to shaped and fired refractories. If it is to be applied to chemically bonded or tar-bonded

bricks, or to unshaped refractory products, they will usually require some form of preliminary heat treatment. This preliminary treatment shall be as agreed between the interested parties and shall be stated in the test report.

#### 5 Apparatus

##### 5.1 Loading device

**5.1.1** The loading device shall have two bearing edges to support the test piece and one for the application of the load. The three bearing edges shall be parallel to each other. For normal test pieces, the distance between the bearing edges supporting the test piece shall be  $125 \pm 2$  mm, with proportionate separations for other test piece lengths (see 6.2). The loading bearing edge shall be placed centrally between the two supporting bearing edges with an accuracy of  $\pm 2$  mm (see the figure).

**5.1.2** The bearing edges and test pieces shall be free from any reaction on contact at the test temperature.

**5.1.3** The bearing edges shall have a length not less than 5 mm greater than the breadth of the test pieces and a radius of curvature of  $5 \pm 1$  mm.

NOTE — Since the bearing edges become flattened with use, they shall be examined periodically to ensure that their radii remain within these limits.

**5.1.4** The distance between the two supporting bearing edges (see the figure) shall be measured at room temperature to an accuracy of  $\pm 0,5$  mm (this value is taken into account in the calculation of the modulus of rupture).

**5.1.5** The loading device shall be capable of applying a load uniformly across the centre of the test piece and of increasing it

<sup>1)</sup> At present at the stage of draft.

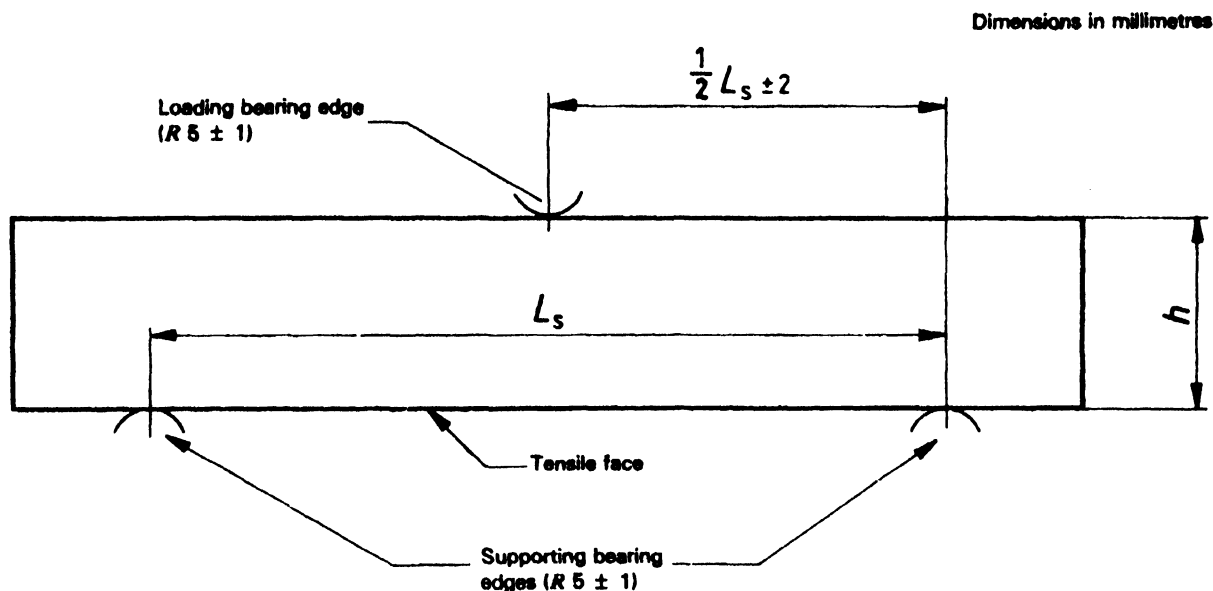


Figure — Arrangement and dimensions of test piece and bearing edges of loading device

at a constant rate. Means shall be provided of recording or indicating the load at failure with an accuracy of  $\pm 2\%$ .

## 5.2 Furnace

5.2.1 The furnace shall be one of the following types:

- a) batch type, in which a number of test pieces are heated to the test temperature together and tested in turn;
- b) sequential type, in which the test pieces are heated to the test temperature one after another as they pass through the apparatus.

5.2.2 In either case, the furnace shall be capable of providing the overall heating of both the bending device and the test pieces, and shall be so designed that at the moment of test the temperature distribution in the test piece is uniform within  $\pm 10^\circ\text{C}$ .

5.2.3 The atmosphere in the furnace shall be air or some other specified gas, as agreed between the parties concerned in the test.

## 5.3 Temperature measuring device

5.3.1 The temperature shall be measured by a calibrated thermocouple in the proximity of the midpoint of the tensile face of the test piece.

5.3.2 The relationship between the measured temperature and the temperature at the midpoint of the tensile face shall first be established and shall be checked periodically in accordance with the procedure set out in the annex.

5.3.3 During the test, the furnace shall be maintained at such a temperature that the midpoint of the tensile face of the test piece is nominally at the required test temperature.

## 6 Number, shape, size and preparation of test pieces

### 6.1 Number

6.1.1 The number of items (bricks) to be tested shall be determined in accordance with ISO 5022 or another standard sampling method agreed between the interested parties.

6.1.2 The number of test pieces to be tested for each item (brick) at each test temperature shall be agreed between the interested parties and shall be the same for each item; it shall be stated in the test report.

### 6.2 Shape and size

6.2.1 Unless otherwise agreed, the test piece shall be a rectangular bar with a cross-section of  $25 \pm 1\text{ mm} \times 25 \pm 1\text{ mm}$  and a length of about 150 mm. The longitudinal faces of each test piece shall be parallel to each other within a tolerance of  $\pm 0,2\text{ mm}$  and the sides of a cross-section of the test piece shall be parallel to each other within a tolerance of 0,1 mm. Care shall be taken to ensure that the test pieces have smooth surfaces and clean edges. If other sizes of test piece are to be used, the dimensions shall be altered in steps of 5 mm, with a minimum of 100 mm for the length and a minimum of 10 mm for the width and for the height.

NOTE — The formula given in 8.1 is only valid for test pieces that are of a slender shape. It is therefore recommended that the ratio of the

height and width of the test piece and the ratio of the height of the test piece to the distance between the supports should be the following<sup>1)</sup>:

$$\frac{h}{L_s} < \frac{1}{4} \quad \text{and} \quad \frac{h}{b} > \frac{1}{3}$$

6.2.2 The breadth and height of the cold test piece shall be measured at its midpoint with an accuracy of  $\pm 0,1$  mm (these values are taken into account in the calculation of the modulus of rupture).

### 6.3 Preparation

6.3.1 If the direction in which the brick was pressed is known, each test piece shall be cut out of the brick in such a way that the upper longitudinal face in the testing position (the face in compression) coincides with or was parallel to one of the original faces of the brick perpendicular to the direction of pressing. No other longitudinal face of a test piece shall include the original skin of the brick.

NOTE — Cutting with a continuous rim diamond wheel is recommended.

If a wheel with a serrated rim is used, the edges of the cut where the wheel emerges are often frayed. It is therefore recommended that in such a case the wheel should enter the face of the brick piece that is to form the tensile faces of the test pieces during the test.

6.3.2 The direction of pressing, if known, shall be marked on each test piece.

6.3.3 The test pieces shall be dried at  $110 \pm 5$  °C to constant mass.

## 7 Test procedure

### 7.1 Heating

7.1.1 The test temperature shall be as agreed between the interested parties. It is recommended that multiples of 100 °C should be used (e.g. 1 000 °C, 1 100 °C, ...), but if necessary multiples of 50 °C may be used.

7.1.2 The test pieces shall be heated to the test temperature  $\pm 10$  °C with a mean rate of heating between 2 °C/min and 10 °C/min and preferably between 4 °C/min and 6 °C/min.

7.1.3 When the test temperature is reached, the test piece shall be maintained at this temperature for sufficient time<sup>2)</sup> for the temperature distribution in it to become uniform within  $\pm 10$  °C. The time allowed for this shall be stated in the test report.

7.1.4 The temperature measured by the thermocouple near the midpoint of the tensile face of the test piece shall not vary during the time of testing by more than  $\pm 2$  °C.

### 7.2 Loading

7.2.1 Place a test piece on the lower bearing edges so that it rests symmetrically across them. If a longitudinal face of a test piece coincides with an original face of the brick, that face shall be the face in compression.

7.2.2 Apply the load vertically on the test piece half-way between the supports in the direction of pressing of the brick, with a constant rate of increase, until failure occurs. The rate of increase of the load shall be calculated, using the formula given in 8.1, so that the rate of increase of tensile stress in the test piece is as follows:

a) for a dense-shaped refractory product:  
 $0,15 \text{ N}\cdot\text{mm}^{-2}\cdot\text{s}^{-1} \pm 10 \%$ ;

b) for an insulating refractory product:  
 $0,05 \text{ N}\cdot\text{mm}^{-2}\cdot\text{s}^{-1} \pm 10 \%$ .

7.2.3 Record the load at which failure of the test piece occurs ( $F_{\text{max}}$ ).

## 8 Calculation and expression of results

8.1 The modulus of rupture ( $\sigma_F$ ) is the ratio of the bending moment at the point of failure ( $M_{\text{max}}$ ) to the moment of resistance  $W$  (the section modulus), and is calculated from the following equation which is derived from Hooke's Law for elastic materials<sup>3)</sup>:

$$\sigma_F = \frac{M_{\text{max}}}{W} = \frac{3}{2} \times \frac{F_{\text{max}} L_s}{bh^2}$$

where

$F_{\text{max}}$  is the maximum force exerted on the test piece;

$L_s$  is the distance between the points of support of the test piece;

$b$  is the breadth of the test piece;

$h$  is the height of the test piece.

8.2 The result shall be expressed in newtons per square millimetre (meganewtons per square metre, megapascals).

1) These are empirical values that have resulted from a study of several publications describing the influence of the dimensions of the test piece on the determination of the modulus of rupture.

2) About 15 to 30 min for normal test pieces of fired bricks. For unfired bricks or unshaped refractories, a pre-treatment or soaking time and temperature shall be agreed between the interested parties.

3) Refractory materials do not always obey Hooke's Law exactly.



## 9 Test report

The test report shall include the following information:

- a) the testing establishment;
- b) the date of test;
- c) a reference to this International Standard, i.e. "Test in accordance with ISO 5013";
- d) designation of bricks (manufacturer, type, shape, batch no., etc.);
- e) the number of items (bricks) tested;
- f) the pre-treatment given to the test pieces (see 7.1.3 and its footnote);
- g) number of test pieces per brick;
- h) dimensions of the test pieces (mm);
- j) position of the test pieces in the brick;
- k) distance between supports (mm);
- m) heating rate ( $^{\circ}\text{C}/\text{min}$ );
- n) atmosphere (see 5.2.3);
- p) test temperature ( $^{\circ}\text{C}$ );
- q) time for which the test temperature was maintained for each test piece (min);
- r) nominal rate of increase of tensile stress for each test piece ( $\text{N}\cdot\text{mm}^{-2}\cdot\text{s}^{-1}$ );
- s) individual values and the median and mean values of the modulus of rupture of each brick.

## Annex

### Measurement of temperature distribution in the test piece

(This annex forms an integral part of the Standard.)

**A.1** Preliminary measurements shall be carried out at each test temperature to determine the following:

- a) the temperature distribution in the test piece;
- b) the time required for the temperature distribution in the test piece to reach the specified degree of uniformity (see 5.2.2 and 7.1.3);
- c) the relation, at equilibrium, between the temperature indicated by the test thermocouple and the temperature at the midpoint of the tensile face of the test piece (see 5.3.1 and 5.3.2).

**A.2** These data can be determined under test conditions using the test thermocouple, additional thermocouples and special test pieces provided with borings for the additional thermocouples. The test pieces shall have the same dimensions as the test pieces to be used (see 6.2) and be of material having nearly the same thermal conductivity as the material to be tested.

**A.3** The measurements shall be carried out on each new furnace and whenever the test conditions have been altered (e.g. after replacement of the heating elements or the test thermocouple).

### **Standard Mark**

The use of the Standard Mark is governed by the provisions of the *Bureau of Indian Standards Act, 1986* and the Rules and Regulations made thereunder. The Standard Mark on products covered by an Indian Standard conveys the assurance that they have been produced to comply with the requirements of that standard under a well defined system of inspection, testing and quality control which is devised and supervised by BIS and operated by the producer. Standard marked products are also continuously checked by BIS for conformity to that standard as a further safeguard. Details of conditions under which a licence for the use of the Standard Mark may be granted to manufacturers or producers may be obtained from the Bureau of Indian Standards;

## Bureau of Indian Standards

BIS is a statutory institution established under the *Bureau of Indian Standards Act, 1986* to promote harmonious development of the activities of standardization, marking and quality certification of goods and attending to connected matters in the country.

### Copyright

BIS has the copyright of all its publications. No part of these publications may be reproduced in any form without the prior permission in writing of BIS. This does not preclude the free use, in the course of implementing the standard, of necessary details, such as symbols and sizes, type or grade designations. Enquiries relating to copyright be addressed to the Director (Publications), BIS.

### Revision of Indian Standards

Amendments are issued to standards as the need arises on the basis of comments. Standards are also reviewed periodically; a standard along with amendments is reaffirmed when such review indicates that no changes are needed; if the review indicates that changes are needed, it is taken up for revision. Users of Indian Standards should ascertain that they are in possession of the latest amendments or edition by referring to the latest issue of 'BIS Handbook' and 'Standards Monthly Additions'. Comments on this Indian Standard may be sent to BIS giving the following reference:

Doc : No. MTD 15 ( 3936 )

### Amendments Issued Since Publication

| Amend No | Date of Issue | Text Affected |
|----------|---------------|---------------|
|          |               |               |
|          |               |               |
|          |               |               |

## BUREAU OF INDIAN STANDARDS

### Headquarters:

Manak Bhavan, 9 Bahadur Shah Zafar Marg, New Delhi 110002  
Telephones : 331 01 31, 331 13 75

Telegrams : Manaksanstha  
( Common to all Offices )

### Regional Offices :

|   | Telephone                                      |
|---|--|
| Central : Manak Bhavan, 9 Bahadur Shah Zafar Marg<br>NEW DELHI 110002   | { 331 01 31<br>331 13 75                       |
| Eastern : 1/14 C. I. T. Scheme VII M, V. I. P. Road, Maniktola<br>CALCUTTA 700054   | { 37 84 99, 37 85 61<br>37 86 26, 37 86 62     |
| Northern : SCO 445-446, Sector 35-C, CHANDIGARH 160036  | { 53 38 43, 53 16 40<br>53 23 84               |
| Southern : C. I. T. Campus, IV Cross Road, MADRAS 600113  | { 235 02 16, 235 04 42<br>235 15 19, 235 23 15 |
| Western : Manakalaya, E9 MIDC, Marol, Andheri ( East )<br>BOMBAY 400093   | { 632 92 95, 632 78 58<br>632 78 91, 632 78 92 |
| Branches : AHMADABAD. BANGALORE. BHOPAL. BHUBANESHWAR. COIMBATORE.<br>FARIDABAD. GHAZIABAD. GUWAHATI. HYDERABAD. JAIPUR. KANPUR.<br>LUCKNOW. PATNA. THIRUVANANTHAPURAM. |  |

**AMENDMENT NO. 1 SEPTEMBER 1994  
TO  
IS 1528 (Part 15) : 1993/ISO 5013 : 1985 METHODS OF  
SAMPLING AND PHYSICAL TESTS FOR  
REFRACTORY MATERIALS  
PART 15 DETERMINATION OF MODULUS OF RUPTURE AT  
ELEVATED TEMPERATURE**

*( Cover page, National Foreword, pages 1, 2, 3 and 4 )* — Substitute 'Part 20' for 'Part 15' wherever it occurs.

( MTD 15 )

---

Reprography Unit, BIS, New Delhi, India

**AMENDMENT NO. 2 DECEMBER 2000  
TO  
IS 1528 ( PART 15 ) : 1991 METHOD OF SAMPLING  
AND PHYSICAL TESTS FOR REFRACTORY  
MATERIALS**

**PART 15 METHOD FOR DETERMINATION OF BULK DENSITY,  
APPARENT POROSITY AND TRUE POROSITY OF DENSE SHAPED  
REFRACTORY MATERIALS**

( Page 2, clause 8.2 ) — Substitute the following formula for the existing:

$$1 \quad \pi_a = \frac{m_3 - m_1}{m_3 - m_2} \times 100$$

2 Amendment No. 1 withdrawn.

( MTD 15 )